

इंटरनेट

मानक

Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

“जानने का अधिकार, जीने का अधिकार”

Mazdoor Kisan Shakti Sangathan

“The Right to Information, The Right to Live”

“पुराने को छोड़ नये के तरफ”

Jawaharlal Nehru

“Step Out From the Old to the New”

IS 10810-63 (1993): Methods of test for cables, Part 63:
Smoke density of electric cables under fire conditions [ETD
9: Power Cables]



“ज्ञान से एक नये भारत का निर्माण”

Satyanarayan Gangaram Pitroda

“Invent a New India Using Knowledge”



“ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है”

Bhartrhari—Nitiśatakam

“Knowledge is such a treasure which cannot be stolen”

BLANK PAGE



भारतीय मानक

केबलों की परीक्षण पद्धतियां

भाग 63 अग्नि अवस्थाओं के अन्तर्गत विद्युत केबलों का धुआं घनत्व मापन

Indian Standard

METHOD OF TESTS FOR CABLES

PART 63 MEASUREMENT OF SMOKE DENSITY OF ELECTRIC CABLES
UNDER FIRE CONDITIONS**1 Scope**

This standard gives the test method for the measurement of smoke emitted when electric cables are burnt under defined conditions.

2 Significance

2.1 The assessment of smoke density is an important factor for evaluating the behaviour of electric cables under fire conditions. The smoke evolved by one or more burning cables is not necessarily reflected by the testing of the individual components and, therefore, test method is recommended for cable assemblies.

2.2 This draft describes the test apparatus and the procedure, but leaves open the question of sample mounting. This is because further experiment is required in order to precisely define the best method for minimum dispersion of results with different operators.

2.3 The draft includes a proposal for standardizing the performance of the test chamber and equipment by the use of a blank test based on a defined volume of smoke.

3 Terminology

3.1 As given in IS 1885 (Part 32) : 1971 'Electrotechnical vocabulary : Part 32 Cable conductors and accessories for electricity supply'.

4 Test Apparatus

4.1 The equipment shall comprise a cubic enclosure with inside dimensions of $3\,000 \pm 30$ mm and constructed for suitable material fixed into a steel angle frame. One side shall have a door, with a glass observation window. Transparent sealed windows (size 100 ± 10 mm x 100 ± 10 mm) shall be provided on two opposite sides to permit the transmission of a beam of light from the horizontal photometric system. The distance from floor to the centre of these windows shall be $2\,150 \pm 100$ mm (see Fig. 1 for plan view).

4.2 The walls of the enclosure shall include orifices for the passage of cables, etc, and to permit the enclosure to be at atmospheric pressure. The total area of the orifices shall not exceed 50 cm^2 . The enclosure should not be directly exposed to sunlight or extreme climatic conditions.

Note — It must be possible to extract fumes from the enclosure after each test through a duct fitted with valve which can be closed during the test. The duct may include a fan to increase the rate of extraction.

4.2.1 The ignition fluid shall be contained in a tray made from galvanized sheet metal with jointed edges, pyramidal trunk or rectangular section, and having the following interior dimensions:

Bottom	$210 \times \pm 10 \times 110 \pm 10$ mm
Top	$240 \pm 10 \times 140 \pm 10$ mm
Height	80 ± 10 mm

July 1993

© BIS 1993

Price Group 4

BUREAU OF INDIAN STANDARDS
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI 110002

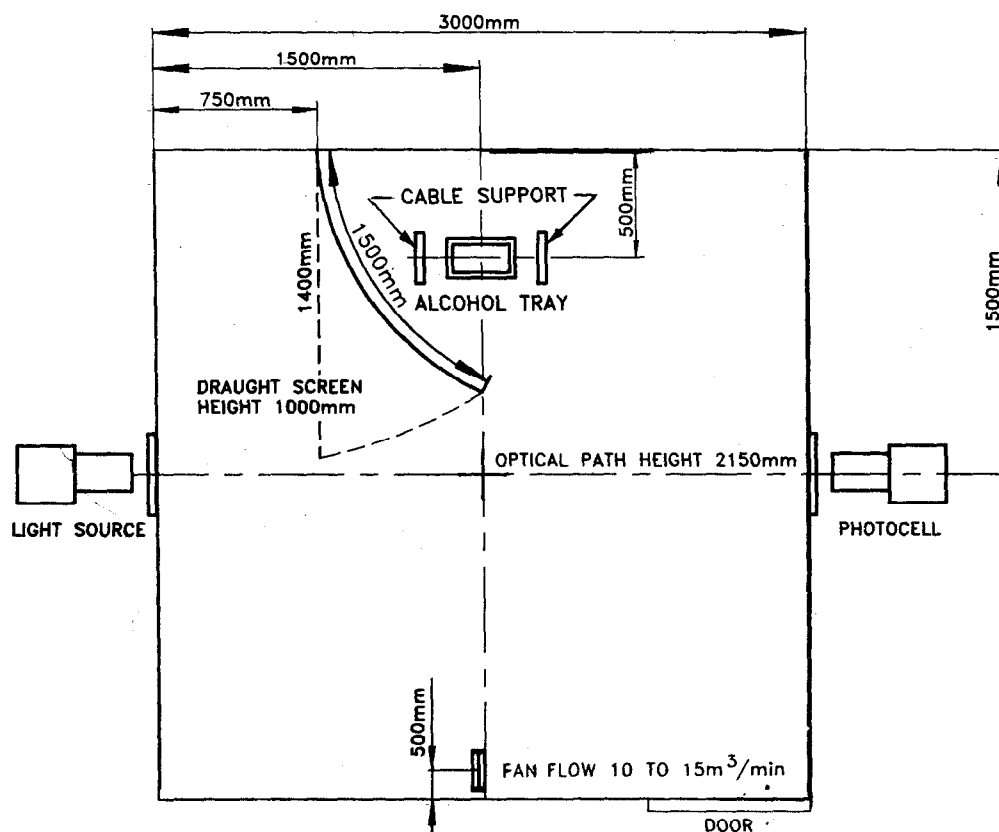


FIG. 1 PLAN VIEW OF TEST CHAMBER

4.2.2 The weight of the tray shall be approximately 250 g.

4.2.3 The tray shall be supported on a metal trestle.

4.3 Smoke Mixing


In order to ensure uniform distribution of the smoke, a table type fan shall be placed on the floor of the cube as shown in Fig. 1. The fan shall have a blade sweep of $300 \text{ mm} \pm 20 \text{ percent}$ and a flow rate of 10 to 15 M³/min. Air shall be blown horizontally by the fan.

4.4 Photometric System

4.4.1 The photometric system is illustrated in Fig. 2. The light source and the receiver shall be placed externally in the centre of two opposite walls of the cube without making physical contact with these walls. The light beam shall traverse the cube through the glass windows in the side walls.

4.4.2 The light source shall be a halogen lamp with a tungsten filament with a clear quartz bulb, having the following characteristics:

Power	100 W
Stabilized voltage	$12 \pm 0.01 \text{ V}$
Nominal luminous flux	2 000 – 2 500 lumens
Nominal colour temperature	2 800 – 3 200 k

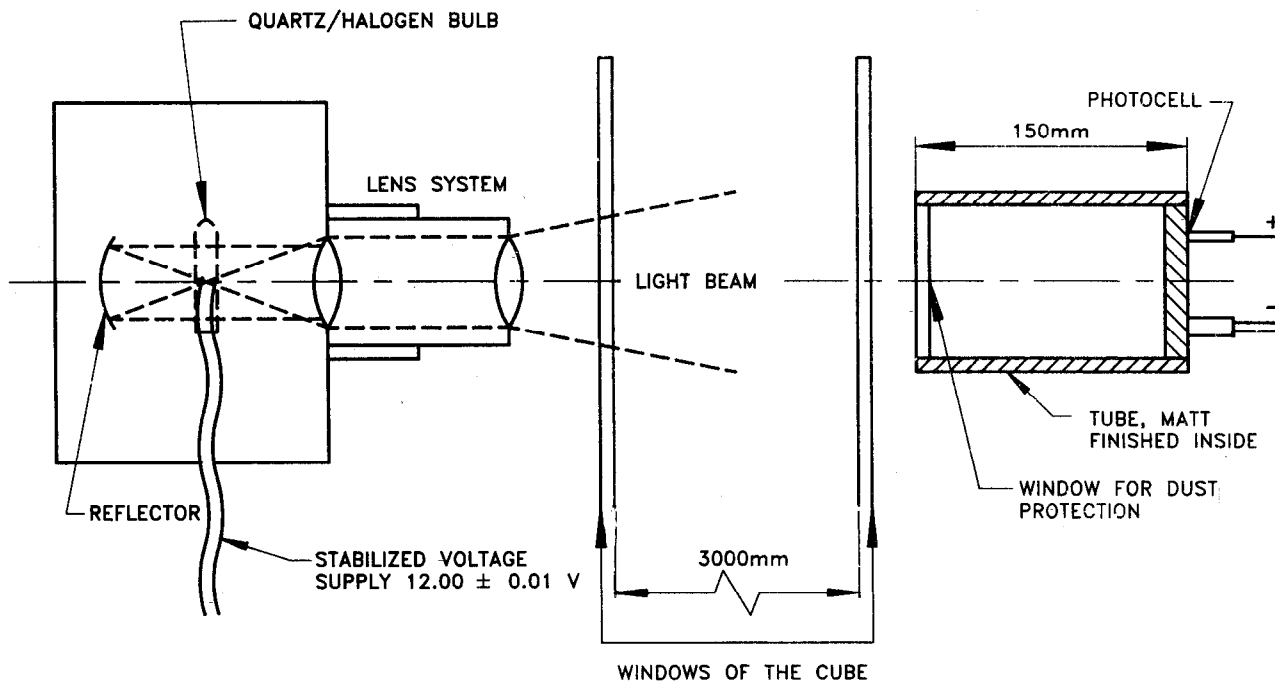

Notes

- 1 The light source and the photocell must be physically isolated from the walls of the cube.
- 2 The diameter of the cone of light on the opposite face from the source of approximately 1.5 m.

FIG. 2 PHOTOMETRIC SYSTEM

4.4.2.1 The lamp shall be mounted in a housing and the beam adjusted by lens system to give an evenly illuminated circular areas of diameter 1.5 ± 0.1 m on the interior of the opposite wall.

4.4.3 The receptor photocell shall be mounted at one end of a 150 ± 10 m tube with a dust protection window at the other end. The inside of the tube shall be matt black to prevent reflections. The photocell shall be connected to a potentiometric recorder to produce a linear proportional output. The cell shall be resistance loaded to operate in its linear range and the input impedance of the recorder should be at least 10 times greater than load resistance of the cell.

5 Material

5.1 Ignition Fluid

The ignition fluid shall be 1 ± 0.01 litres of distilled alcohol, having the following composition:

Ethanol	90 ± 1 percent
Methanol	4 ± 1 percent
Water	6 ± 1 percent

6 Test Specimen

6.1 The size and number of test pieces and their assembly is given in 6.2 to 6.4.

Note – The method of handling some samples of large diameter cables has been shown to influence the results significantly. For example, identical cable selected from drums having differing barrel dimensions may produce different values of absorbance. Where more than one test piece is involved, it is essential to define their disposition and whether they are bound tightly or unbound or precisely spaced. Where cables are small, that is 10 mm in diameter, their disposition in the test assembly must be defined because a substantial number are normally involved offering many possible arrangements.

6.2 Lengths of cable, measuring $1\,000 \pm 50$ mm shall be carefully straightened.

6.3 Number of Test Specimen

10 mm dia	Under consideration
10 mm to 25 mm dia	3
25 mm to 40 mm dia	2
40 mm dia	1

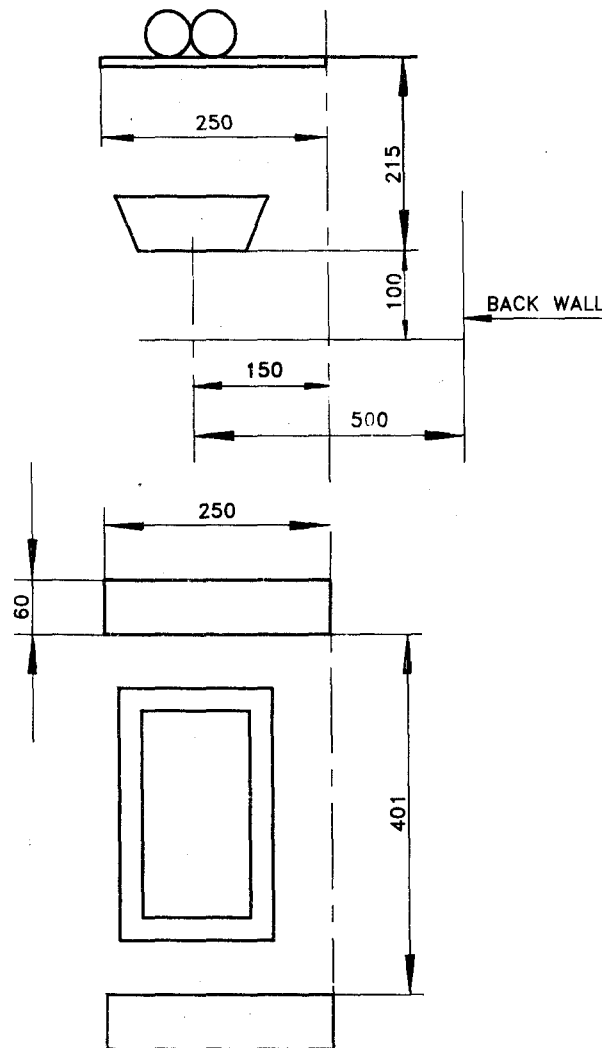


FIG. 3 METHOD OF SUPPORT OF TEST PIECE

6.4 Assembly of Test Piece

6.4.1 The assembly shall be tested as a flat horizontal unit placed symmetrically above the tray by means of vertical supports equipped with horizontal brackets (Fig. 3) such that the vertical distance of the bottom of the test assembly from the bottom of the tray is 215 ± 5 mm.

6.4.2 The bundles or the individual test pieces shall be held together in close contact throughout the length. The binders shall be metallic and placed at the ends of 300 ± 20 mm from each end of the test piece.

7 Conditioning

7.1 The cable sample shall be conditioned for at least 24 hours at $27 \pm 2^\circ\text{C}$.

8 Procedure

8.1 Calibration of the Test Equipment

8.1.1 In order to ensure that results with different apparatus are comparable, it is essential to eliminate any dispersion in results caused by deviation in the test apparatus. A standardization procedure as given in Annex A uses a defined density of smoke.

8.1.2 The photometric system is energized before the blank test (see 8.3). When stability has been attained, the zero and full scale reading of the recorder shall be adjusted to correspond respectively to 0 and 100 percent transmission of the light. The full reading of the recorder corresponding 100 percent transmission of the light represents I_0 , the initial transmittance.

Note — Periodically, it is necessary to verify the performance of the photocell by placing in the light beam standard neutral density filters which must cover the entire optical entry part of the photocell. The values of absorbance (or optical density) measured by the photocell must fall within ± 5 percent of the standard values. The filters shall also permit the verification of linearity of response of the detector which must be proportional to the absorbance of light in the range used.

8.2 In order to avoid the effect of humidity deforming the absorbance level a blank test is carried out prior to any single test of series of tests carried out in rapid succession.

8.3 Ignite 1 ± 0.01 litre of alcohol (see 5.1) in the tray with no cables' place. The door of the cube is left partly open to allow air to enter the enclosure. The cube shall then be purged of all combustion products by operating the extraction system.

8.4 The interior temperature of the test cube shall measure $30 \pm 5^\circ\text{C}$ prior to the beginning of each test.

8.5 The following series of operation are carried out :

- a) Close the valve in the extraction system;
- b) Place test piece on its support;
- c) Measure alcohol and pour into tray (see Fig. 1);
- d) Start the air circulation fan;
- e) Ignite the alcohol, start chronometer and chart recorder; and
- f) Close door.

- 8.6**
- a) The test is finished when there is no change in light transmittance for 5 minutes after the source has extinguished;
 - b) Remove test piece for observation;
 - c) Purge the cube of combustion products prior to the next test; and
 - d) If no blank test is to be performed, it may be necessary to clean the windows of the photometric system to regain 100 percent transmission after stabilization of the voltage.

9 Tabulation of Observation

External Dia of Cable	Number of Cables n	Initial Light Transmittance I_0	Final Light Transmittance I_t
--------------------------	----------------------------	---	---------------------------------------

10 Calculation

10.1 The standard absorbance (A_0) is calculated as under :

$$\text{Measured absorbance } (A_m) = \log_{10} \frac{I_0}{I_t}$$

Standard absorbance across 1 metre cube :

$$A_o = \frac{A_m \times \text{cube factor}}{n}$$

$$\text{where cube factor} = \frac{\text{Volume of cube(m}^3\text{)}}{\text{Length of light path(m)}}$$

n = Number of individual cables.

11 Report

11.1 The result obtained are reported as under:

<i>Designation of Material</i>	<i>Measured Absorbance</i>	<i>Standard Absorbance</i>
--------------------------------	----------------------------	----------------------------

11.2 The following criteria should be used in judging acceptability of smoke density rating data:

11.2.1 Repeatability

Two individual results (not average) determined by a single operator in one laboratory should not be considered suspect (at 95 percent confidence level) unless they differ by more than 18 percent absolute.

11.2.2 Reproducibility

Two results from different laboratories (based on the average of three tests) should not be considered suspect (at 95 percent confidence level) unless they differ by more than 15 percent absolute.

ANNEX A

(Clause 8.1)

CALIBRATION ON TEST APPARATUS

A-1 Preparation of Test Solution

A-1.1 Solutions of one litre of toluene mixed with the alcohol used for the test shall be made up in the following respective volumes 4 : 96 and 10 : 90, using a pipette and a volumetric flask for accuracy of measurement.

A-1.2 Test Procedure

Follow the procedure for the blank test (8.3) noting the transmittance level (I_i) at the end of the test.

A-1.3 Verification Procedure

Calculate the measured absorbance (A_m) as follows:

$$A_m = \log_{10} \frac{I_o}{I_i}$$

where

I_o = Initial transmittance.

Calculate the standard absorbance (A_o)

$$A_o = \frac{A_m}{\text{Percent tolouence}} \times \frac{\text{Volume of cube(m}^3\text{)}}{\text{Optional path length (m)}}$$

Recommended values of A_o are :

4 percent Toluene	0.18 to 0.26
10 percent Toluene	0.80 to 1.20

EXPLANATORY NOTE

The standard has been prepared by referring to IEC Doc : 20 (Secretariat) 212.